


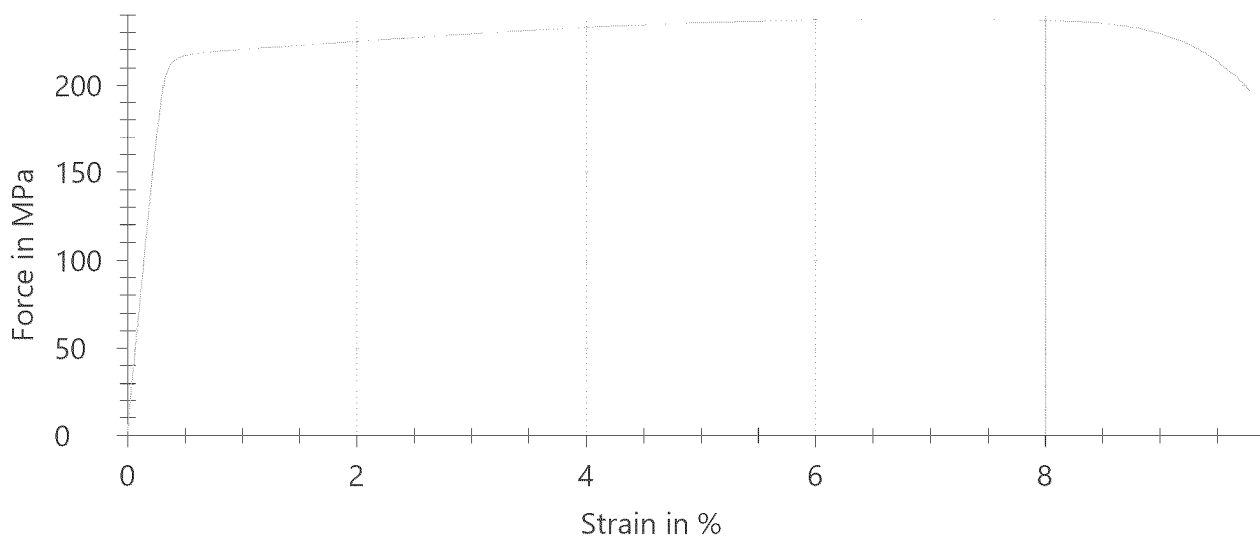
Test report

Customer : Be Group Oy Ab	Alloy : 6063 T6
Order No. : 200009/7822	Tester : Juha Matintupa
POS : 30	Notes : P097000/lina Lehtovuori
Profile No. : 439 SP 30x20x1.5	
Pre-load : 2 MPa	Speed in the yield range : 0.00025 1/s
Speed, Young's modulus : 5 MPa/s	Test speed : 0.008 1/s
Speed, yield point : 60 MPa/s	

Test results:

Legend	No.	E GPa	R _{p0.2} MPa	R _m MPa	A _{50mm} %	A _{manual} %	S ₀ mm ²	Conduct.(MS/m)
	1	66.0	217.2	237.7	9.5	9.0	16.33	31.3

Series graph:



Statistics:

Series	E GPa	R _{p0.2} MPa	R _m MPa	A _{50mm} %	A _{manual} %	S ₀ mm ²	Conduct.(MS/m)
n = 1							
\bar{x}	66.0	217.2	237.7	9.5	9.0	16.33	31.3
s	-	-	-	-	-	-	-
v [%]	-	-	-	-	-	-	-